

Resistance of SAF™ Materials to Automotive Chemicals


The results are included in this white paper.

Introduction

The aim of this document is to give customers an indication of the performance of Stratasys® High Yield PA11, SAF PA12, and SAF PP under exposure to common automotive chemicals.

The reagents tested were:

- Battery acid
- Antifreeze
- Synthetic motor oil
- Silicone grease
- Petroleum grease
- Screen wash
- Distilled water
- Petrol
- Diesel

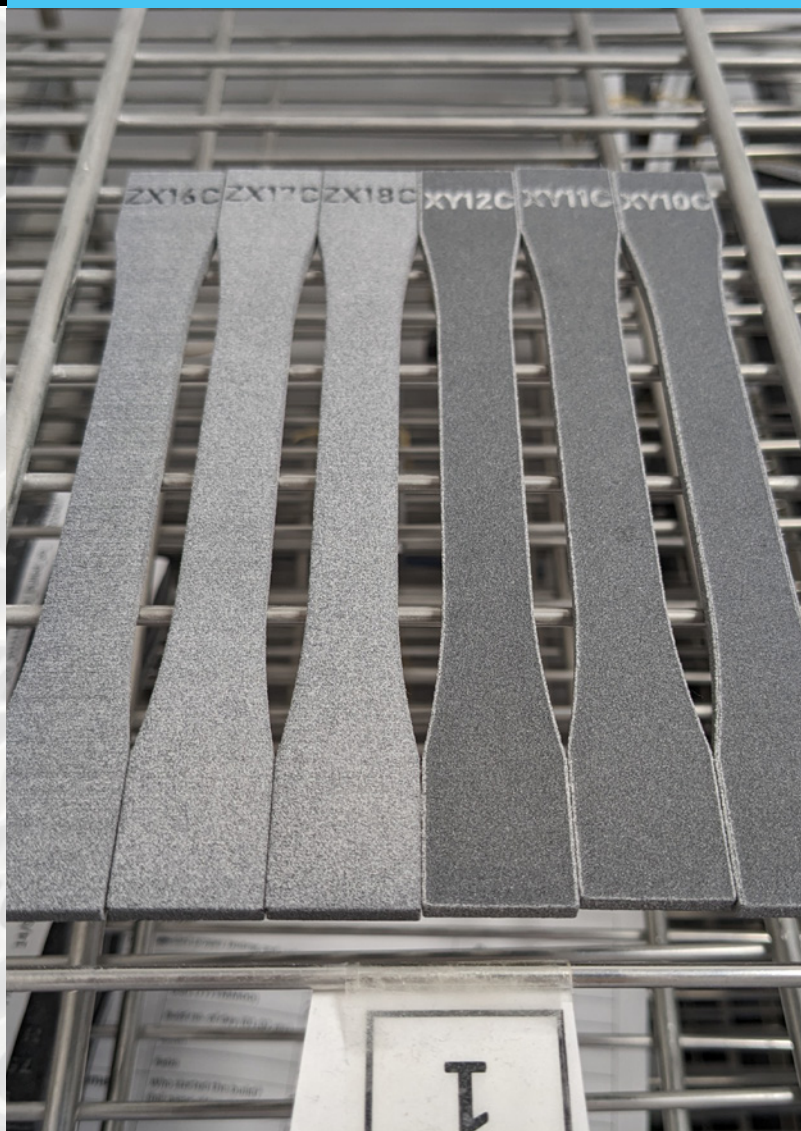



Methodology

The experiment was carried out in accordance with ASTM D543 which defines a standard practice of evaluating the resistance of plastics to chemical reagents.

Specimens were created using Stratasys H350™ SAF™ 3D printers, with both vertical (ZX) and horizontal (XY) print orientations tested. The two specimen types used in the test were:

- ASTM D638 Type 1 tensile bars, to evaluate changes to mechanical properties
- 50.80mm x 3.175mm discs, to evaluate dimensional and weight changes


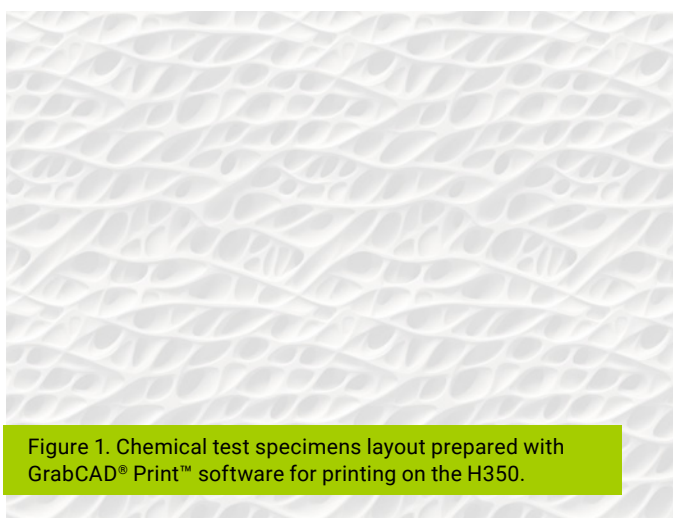


Figure 1. Chemical test specimens layout prepared with GrabCAD® Print™ software for printing on the H350.

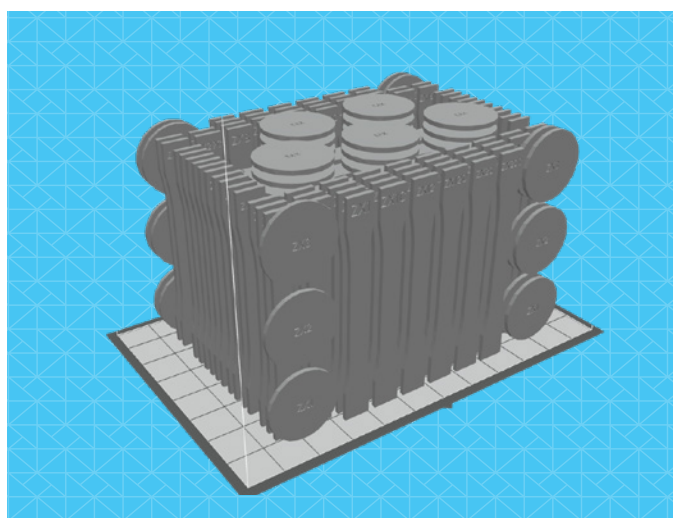

For each experiment, all specimens were preconditioned at 23°C and 50% relative humidity for a minimum of 40 hours before contact with the reagent. Control specimens remained on the preconditioning racks for the duration of the experiment (Figure 2), while test specimens were submerged in a 4L reagent bath for 168 hours (1 week).





Figure 2. Tensile control specimens (marked C with matching pair number) on preconditioning racks.

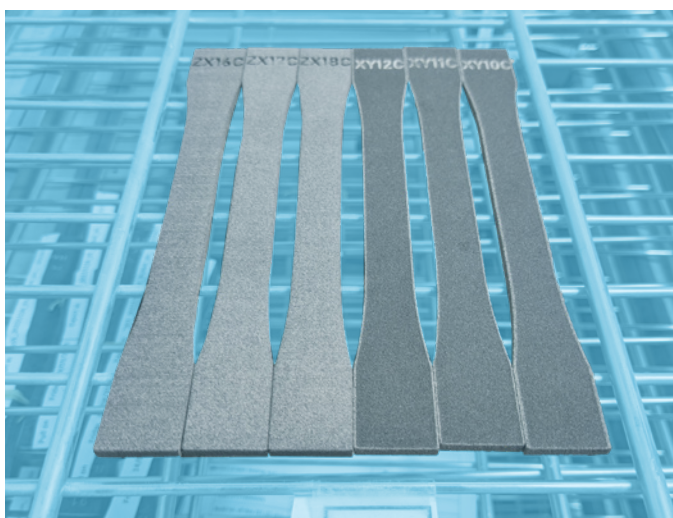

Frames were fabricated from stainless steel and nichrome wire to hold the specimens in place without touching the container walls or each other during immersion in reagent (Figure 3).

A magnetic stir bar was also placed within the container before sealing the experiment. This was used to agitate the reagent for 30 minutes at six 24-hour intervals before removal of the parts at 168 hours. A digitally timed magnetic stir plate (Figure 4) ensured a consistent stirring time across all experiments.

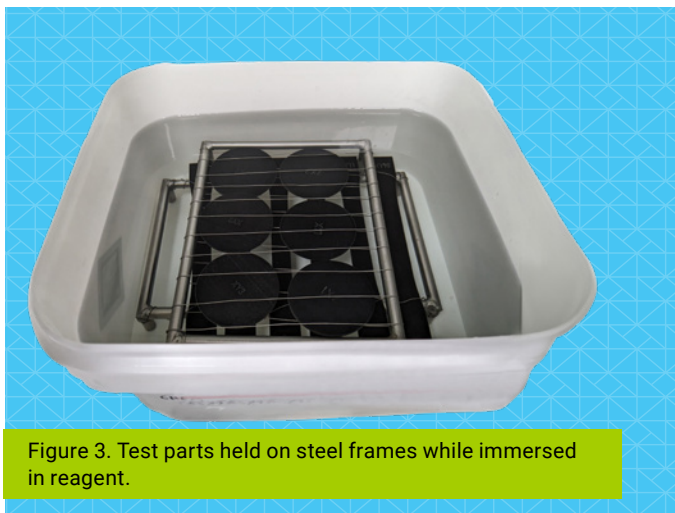


Figure 3. Test parts held on steel frames while immersed in reagent.



Figure 4. Sealed experiment container resting on the digitally timed magnetic stirring plate.

The previously described method would be impractical for silicone and petroleum grease. Instead, a thick spray coating of reagent at the start of each test was opted for, followed by a thin re-application every 24 hours. Parts were checked visually for even coverage on each application.

Tensile Specimens

Tensile tests were carried out on a Tinius Olsen 10ST universal testing setup (Figure 5) in accordance with ASTM D638. These tests were carried out within 30 minutes of removal from the reagent bath.



Figure 5. Tensile testing apparatus used.

A total of 12 specimens were tested per reagent. This consisted of six parts immersed in reagent, while six parts were held from the same build to provide control values for the test. Control parts were printed adjacent to their respective test parts.



Weight and Dimension Discs

Weight and dimension tests compared pre- and post-immersion values of disc-shaped specimens (Figure 6). Weights were measured using an A&D HR-100AZ analytical balance. Thickness and diameter values were measured manually using a micrometer and digital callipers, respectively. A total of six weight and dimension parts were tested per reagent.

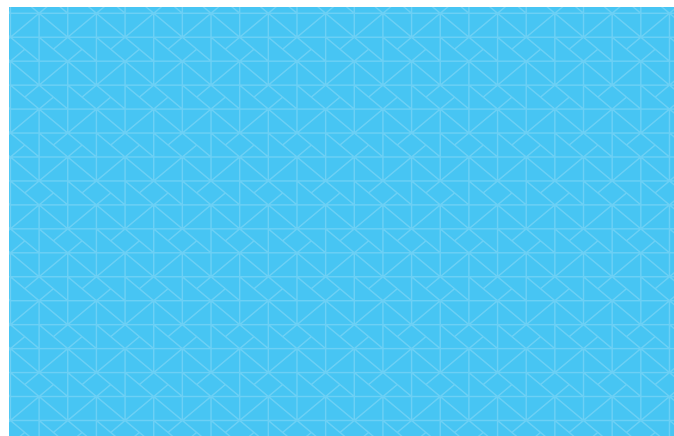
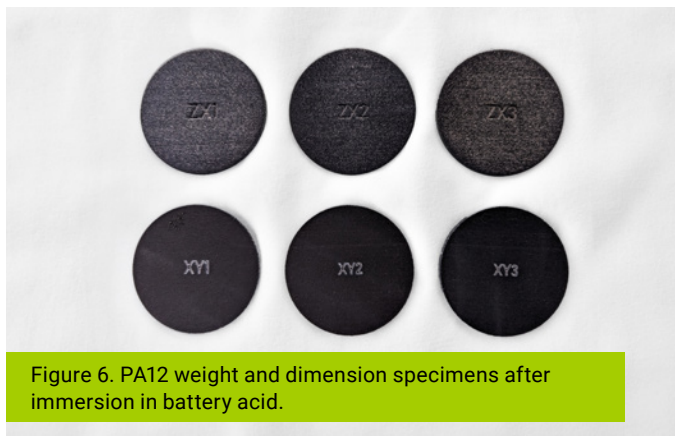



Figure 6. PA12 weight and dimension specimens after immersion in battery acid.

All weight and dimension discs were kept a further 168 hours on preconditioning racks after removal from reagent; then were re-weighed to investigate how parts dry after contact with these chemicals.

Graphs of % Change Per Property

PA11 Results


As a Stratasys preferred material, standard deviation values are available from our High Yield PA11 Datasheet. These are indicated by the black dashed lines.

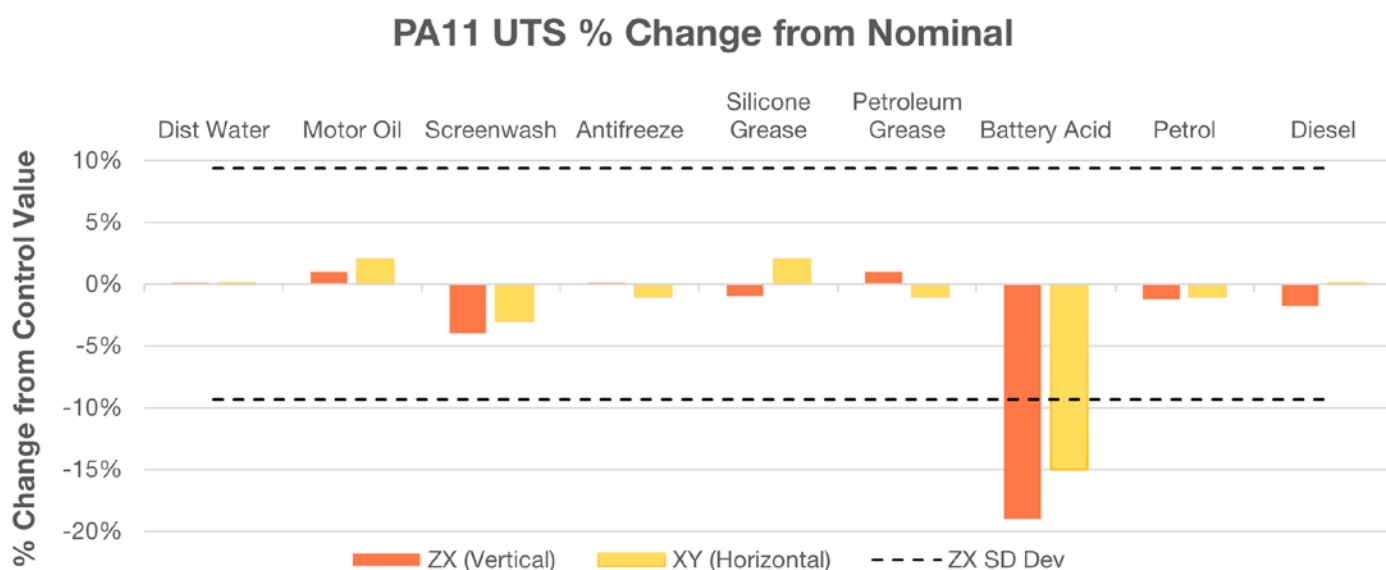




PA11 Results (continued)

PA11 Youngs Modulus % Change from Nominal

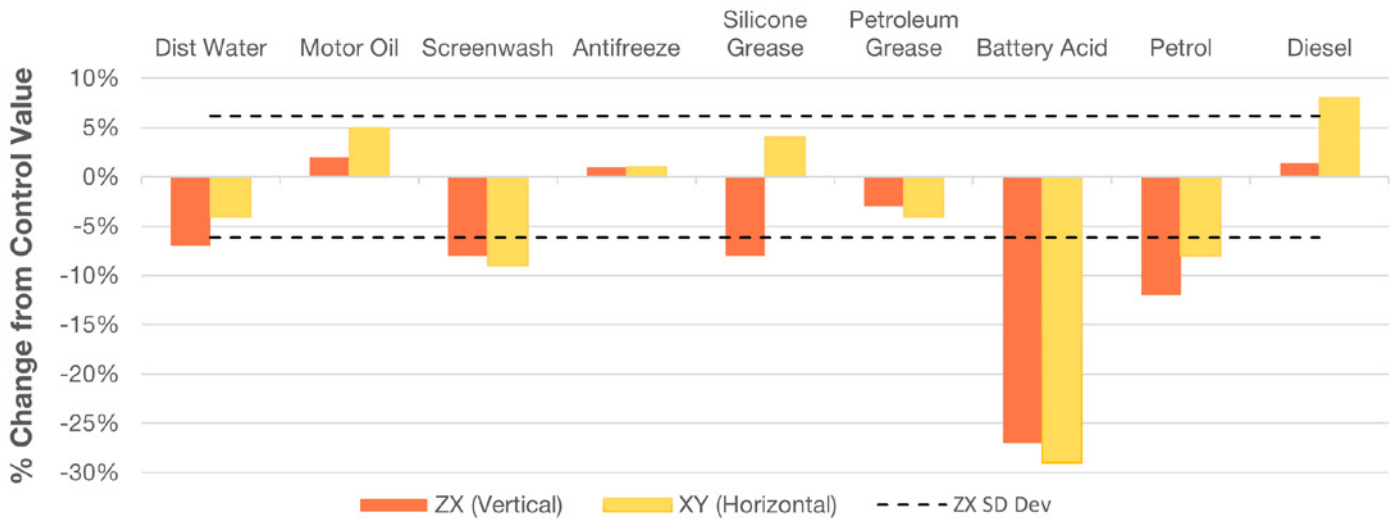

PA11 Elongation at Break % Change from Nominal

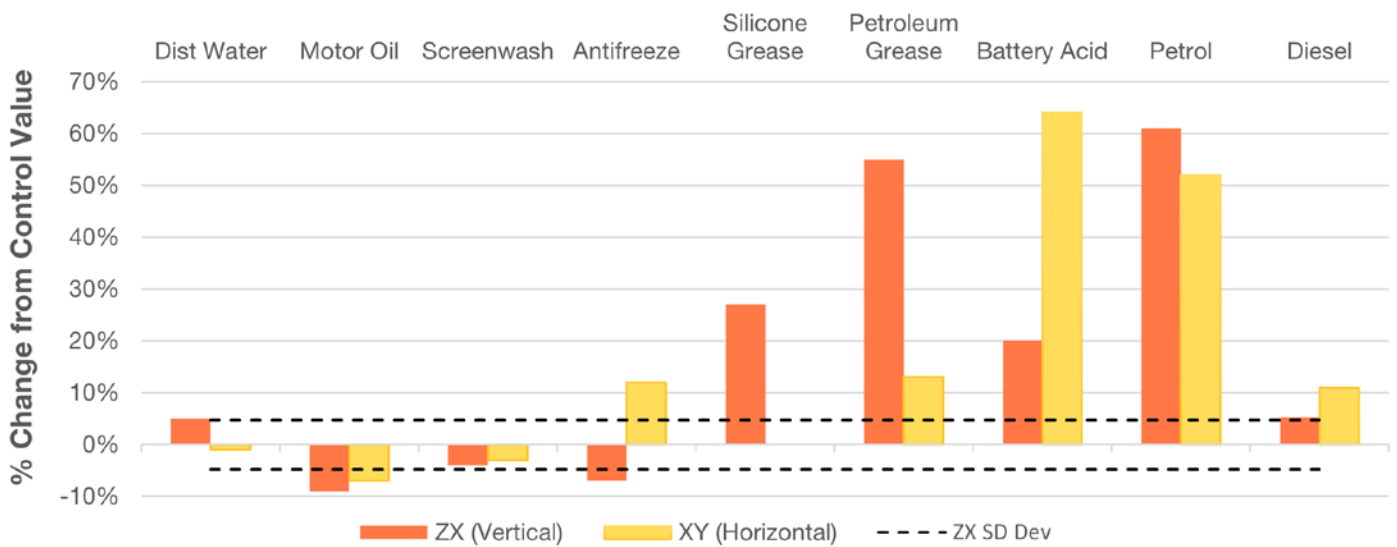




Graphs of % Change Per Property


PA12 Results

Indicative standard deviation values are provided on the graphs by the black dashed lines.

PA12 UTS % Change from Nominal

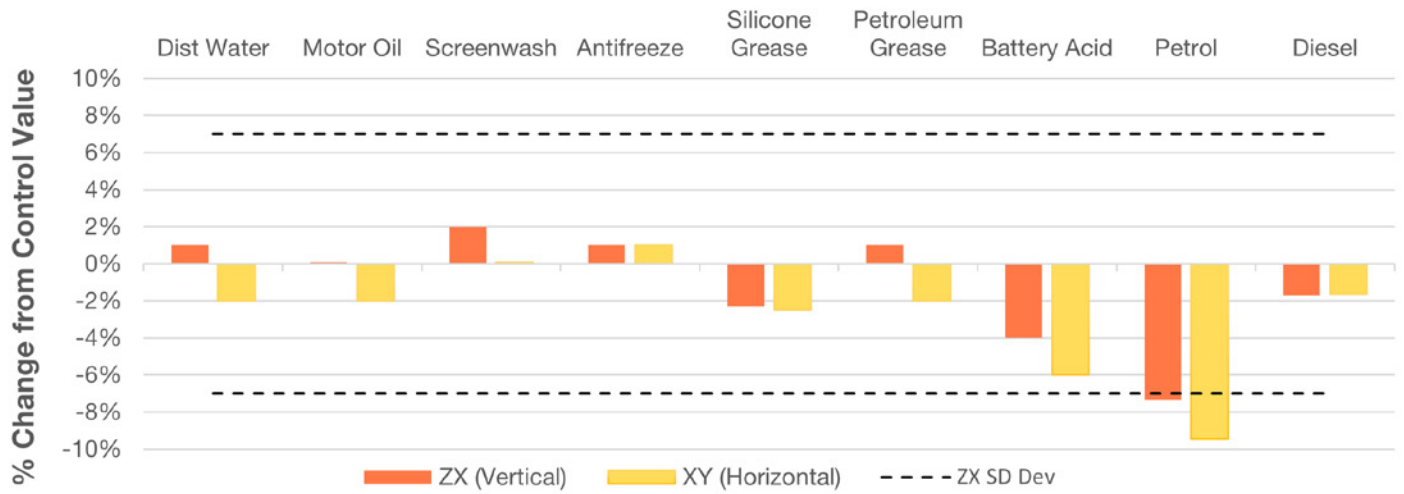


PA12 Youngs Modulus % Change from Nominal

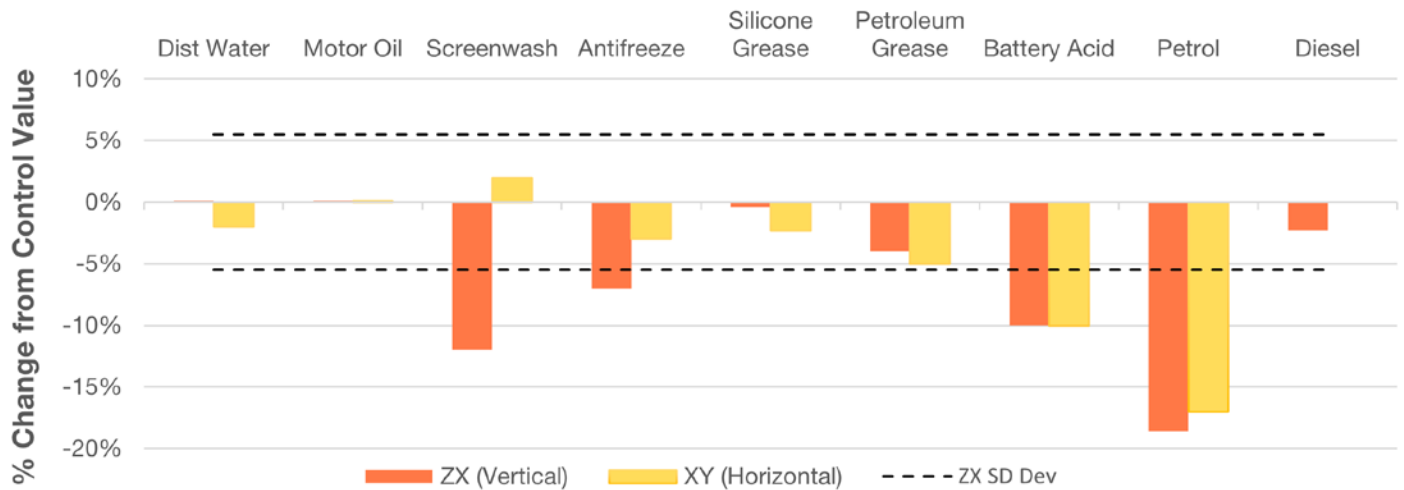



PA12 Results (continued)

PA12 Elongation at Break % Change from Nominal

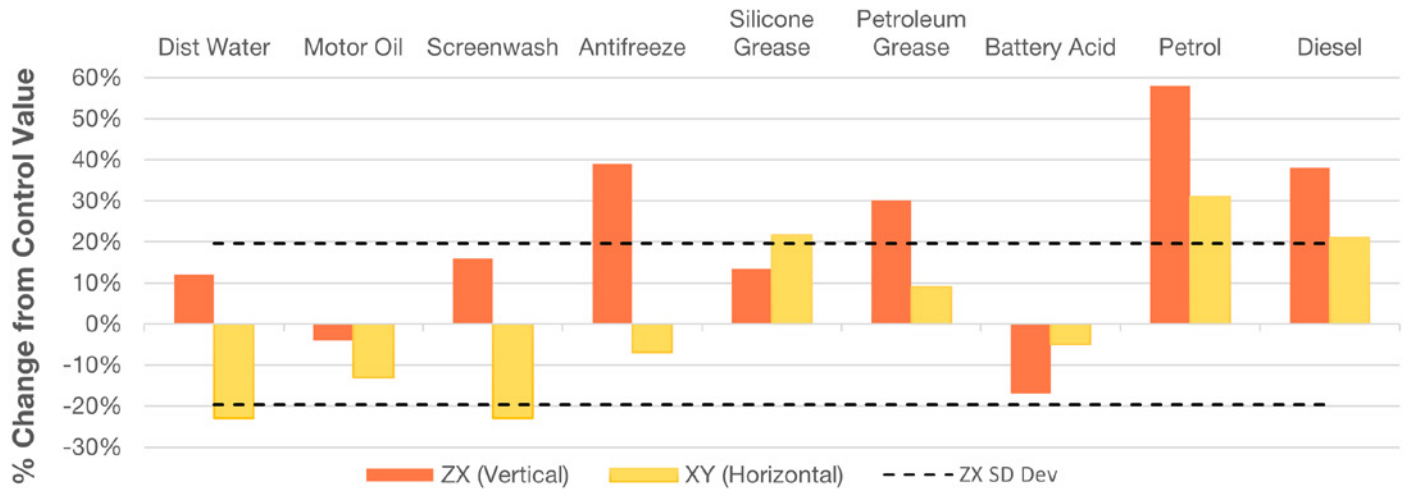




Graphs of % Change Per Property


PP Results

As a Stratasys preferred material, standard deviation values are available from the SAF PP Datasheet. These are indicated by the black dashed lines.

PP UTS % Change from Nominal

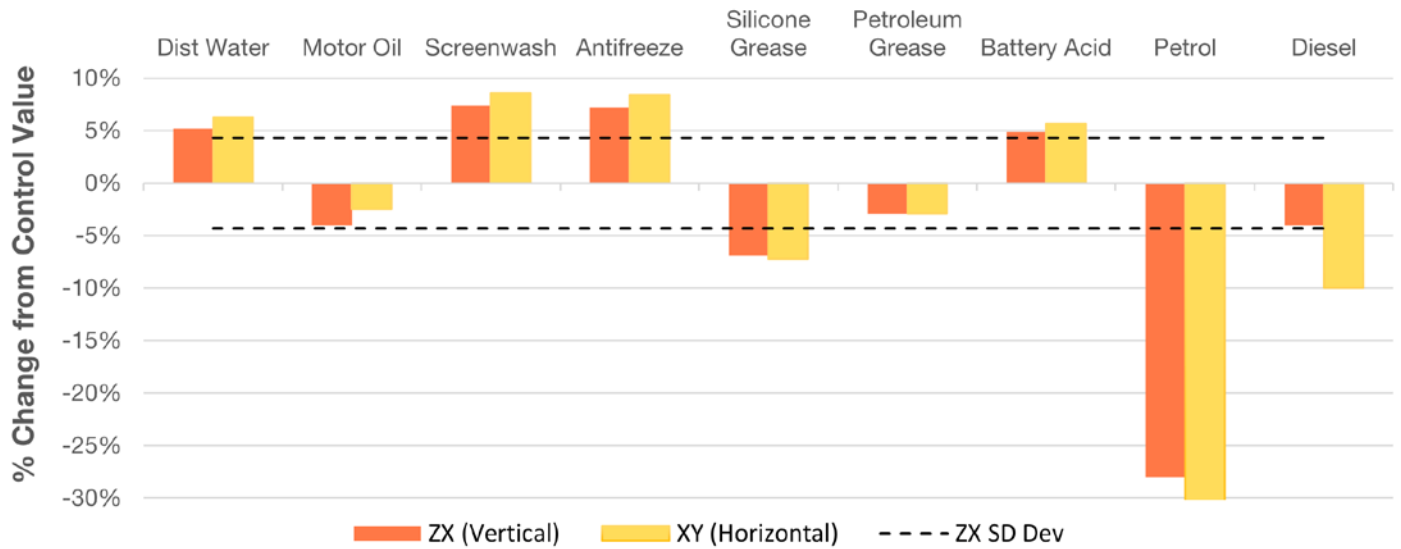


PP Youngs Modulus % Change from Nominal

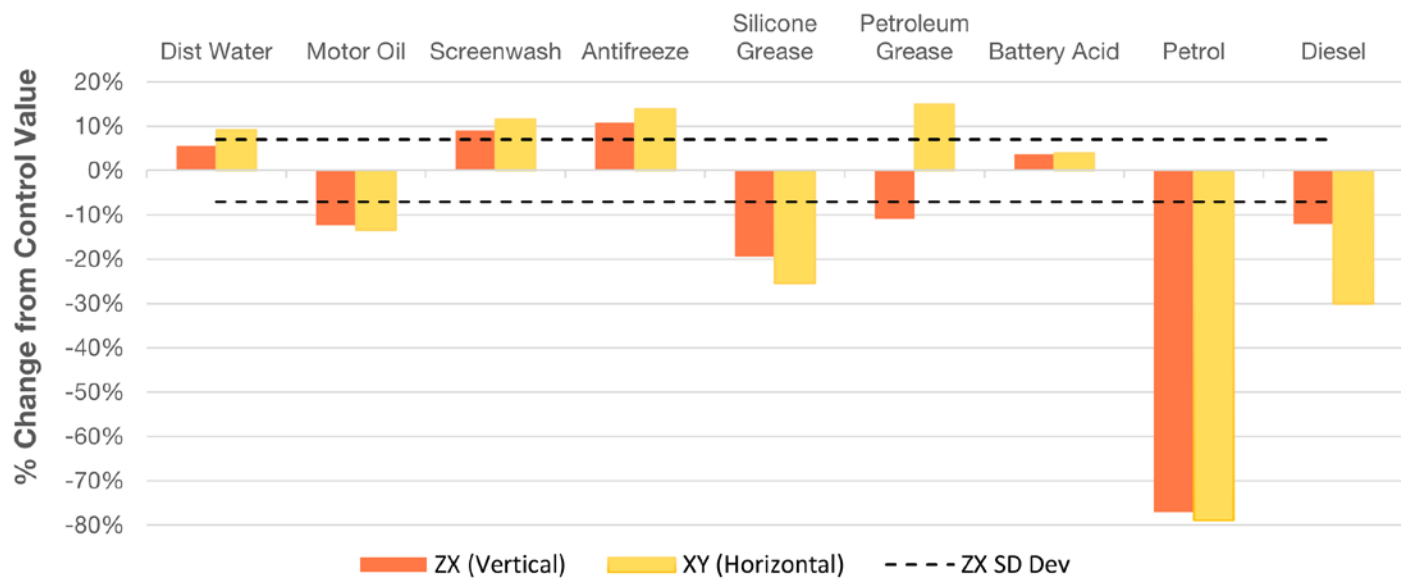



PP Results (continued)

PP Elongation at Break % Change from Nominal

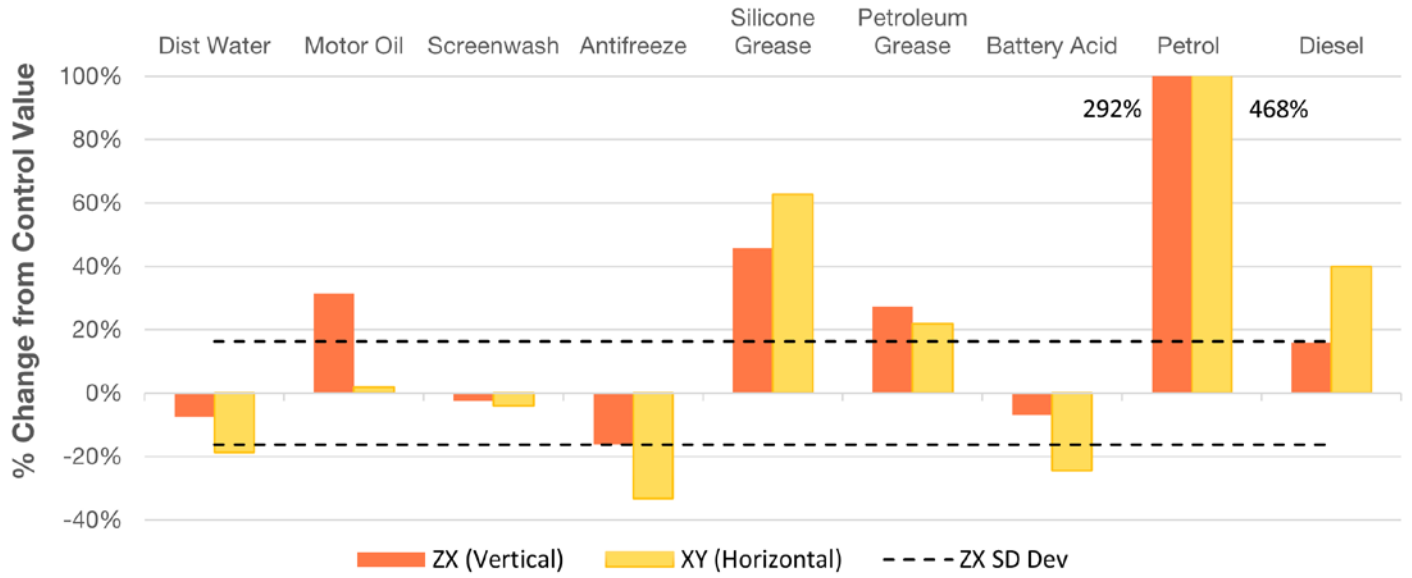



Tables of Final Results

PA11 Change in Mechanical Properties - 168 hr Exposure (ASTM D543)

	Reagent	ZX % Change	XY % Change
UTS (MPa)	Dist Water	0%	0%
	Motor Oil (Synth)	+1%	+2%
	Screenwash	-4%	-3%
	Antifreeze	0%	-1%
	Silicone Grease	-1%	+2%
	Petro Grease	+1%	-1%
	Battery Acid	-19%	-15%
	Petrol (Gasoline)	-1%	-1%
	Diesel	-2%	0%
Modulus (MPa)	Dist Water	-7%	-4%
	Motor Oil (Synth)	+2%	+5%
	Screenwash	-8%	-9%
	Antifreeze	+1%	+1%
	Silicone Grease	-8%	+4%
	Petro Grease	-3%	-4%
	Battery Acid	-27%	-29%
	Petrol (Gasoline)	-12%	-8%
	Diesel	+1%	+8%
EaB (%)	Dist Water	+5%	-1%
	Motor Oil (Synth)	-9%	-7%
	Screenwash	-4%	-3%
	Antifreeze	-7%	+12%
	Silicone Grease	+27%	0%
	Petro Grease	+55%	+13%
	Battery Acid	+20%	+64%
	Petrol (Gasoline)	+61%	+52%
	Diesel	+5%	+11%

High Yield PA11 Reference Values

Property (Orientation)	Mean Value
Tensile Strength (ZX)	47 MPa
Tensile Strength (XZ, YX)	51 MPa
Elongation at Break (ZX)	11 %
Elongation at Break (XZ, YX)	30 %
Tensile Modulus (ZX)	1609 MPa
Tensile Modulus (XZ, YX)	1529 MPa



Tables of Final Results

PA12 Change in Mechanical Properties - 168 hr Exposure (ASTM D543)

	Reagent	ZX % Change	XY % Change
UTS (MPa)	Dist Water	+1%	-2%
	Motor Oil (Synth)	0%	-2%
	Screenwash	+2%	0%
	Antifreeze	+1%	+1%
	Silicone Grease	-2%	-3%
	Petro Grease	+1%	-2%
	Battery Acid	-4%	-6%
	Petrol (Gasoline)	-7%	-9%
	Diesel	-2%	-2%
Modulus (MPa)	Dist Water	0%	-2%
	Motor Oil (Synth)	0%	0%
	Screenwash	-1%	+2%
	Antifreeze	-7%	-3%
	Silicone Grease	0%	-2%
	Petro Grease	-4%	-5%
	Battery Acid	-10%	-10%
	Petrol (Gasoline)	-19%	-17%
	Diesel	-2%	0%
EaB (%)	Dist Water	+12%	-23%
	Motor Oil (Synth)	-4%	-13%
	Screenwash	+16%	-23%
	Antifreeze	+39%	-7%
	Silicone Grease	+14%	+22%
	Petro Grease	+30%	+9%
	Battery Acid	-17%	-5%
	Petrol (Gasoline)	+58%	+31%
	Diesel	+38%	+21%

SAF PA12 Reference Values

Property (Orientation)	Mean Value
Tensile Strength (ZX)	46 MPa
Tensile Strength (XZ, YX)	47 MPa
Elongation at Break (ZX)	5 %
Elongation at Break (XZ, YX)	11 %
Tensile Modulus (ZX)	1700 MPa
Tensile Modulus (XZ, YX)	1750 MPa

Note: small elongation values are due to the stiffness of PA12. As a result, this test is more susceptible to noise and may see large percentage changes over this limited sample size.



Tables of Final Results

PP Change in Mechanical Properties - 168 hr Exposure (ASTM D543)

	Reagent	ZX % Change	XY % Change
UTS (MPa)	Dist Water	+5%	+6%
	Motor Oil (Synth)	-4%	-3%
	Screenwash	+7%	+9%
	Antifreeze	+7%	+8%
	Silicone Grease	-7%	-7%
	Petro Grease	-3%	-3%
	Battery Acid	+5%	+6%
	Petrol (Gasoline)	-28%	-36%
	Diesel	-4%	-10%
Modulus (MPa)	Dist Water	+6%	+9%
	Motor Oil (Synth)	-12%	-13%
	Screenwash	+9%	+12%
	Antifreeze	+11%	+14%
	Silicone Grease	-19%	-25%
	Petro Grease	-11%	+15%
	Battery Acid	+4%	+4%
	Petrol (Gasoline)	-77%	-79%
	Diesel	-12%	-30%
EaB (%)	Dist Water	-8%	-19%
	Motor Oil (Synth)	+31%	+2%
	Screenwash	-2%	-4%
	Antifreeze	-16%	-33%
	Silicone Grease	+46%	+63%
	Petro Grease	+27%	+22%
	Battery Acid	-7%	-25%
	Petrol (Gasoline)	+292%	+468%
	Diesel	+16%	+40%

SAF PP Reference Values

Property (Orientation)	Mean Value
Tensile Strength (ZX)	25.8 MPa
Tensile Strength (XZ, YX)	25.8 MPa
Elongation at Break (ZX)	10.7 %
Elongation at Break (XZ, YX)	22.5 %
Tensile Modulus (ZX)	1212 MPa
Tensile Modulus (XZ, YX)	1260 MPa



Tables of Final Results

PA11 Change in Dimensions and Weight - 168 hr Exposure (ASTM D453)

	Reagent	ZX % Change	XY % Change
Diameter	Dist Water	0.0%	0.0%
	Motor Oil (Synth)	0.0%	0.0%
	Screenwash	0.0%	0.0%
	Antifreeze	0.1%	-0.1%
	Silicone Grease	0.0%	0.0%
	Petro Grease	0.0%	0.0%
	Battery Acid	0.4%	0.4%
	Petrol (Gasoline)	0.1%	0.3%
	Diesel	0.1%	0.0%
Thickness	Dist Water	0.2%	0.7%
	Motor Oil (Synth)	0.0%	-0.5%
	Screenwash	0.2%	1.0%
	Antifreeze	0.0%	0.1%
	Silicone Grease	-0.4%	-0.2%
	Petro Grease	0.1%	0.3%
	Battery Acid	7.0%	6.6%
	Petrol (Gasoline)	0.6%	0.5%
	Diesel	-0.7%	0.0%
Weight	Dist Water	1.0%	0.6%
	Motor Oil (Synth)	1.0%	0.4%
	Screenwash	0.3%	0.3%
	Antifreeze	0.9%	0.4%
	Silicone Grease	1.0%	0.6%
	Petro Grease	1.8%	1.0%
	Battery Acid	13.3%	13.0%
	Petrol (Gasoline)	1.2%	1.2%
	Diesel	0.5%	0.2%
Weight (168hrs Dried)	Dist Water	0.2%	0.2%
	Motor Oil (Synth)	1.0%	0.5%
	Screenwash	0.3%	0.4%
	Antifreeze	0.2%	0.2%
	Silicone Grease	0.2%	0.2%
	Petro Grease	1.6%	0.9%
	Battery Acid	11.5%	10.9%
	Petrol (Gasoline)	0.6%	0.7%
	Diesel	0.2%	0.1%



Tables of Final Results

PA12 Change in Dimensions and Weight - 168 hr Exposure (ASTM D453)

	Reagent	ZX % Change	XY % Change
Diameter	Dist Water	0.1%	0.1%
	Motor Oil (Synth)	0.0%	0.0%
	Screenwash	0.0%	0.0%
	Antifreeze	0.0%	0.0%
	Silicone Grease	0.0%	0.0%
	Petro Grease	0.0%	0.0%
	Battery Acid	0.1%	0.1%
	Petrol (Gasoline)	0.3%	0.2%
	Diesel	0.1%	0.0%
Thickness	Dist Water	0.1%	0.1%
	Motor Oil (Synth)	-0.4%	-0.1%
	Screenwash	-0.1%	0.0%
	Antifreeze	-0.4%	0.1%
	Silicone Grease	0.1%	0.2%
	Petro Grease	2.4%	0.6%
	Battery Acid	1.1%	1.3%
	Petrol (Gasoline)	0.6%	0.4%
	Diesel	0.0%	-0.3%
Weight	Dist Water	-2.1%	-1.0%
	Motor Oil (Synth)	1.0%	0.7%
	Screenwash	0.7%	0.5%
	Antifreeze	1.4%	1.1%
	Silicone Grease	1.0%	0.5%
	Petro Grease	1.8%	1.2%
	Battery Acid	3.9%	3.8%
	Petrol (Gasoline)	1.2%	1.2%
	Diesel	0.7%	0.6%
Weight (168hrs Dried)	Dist Water	2.3%	-2.1%
	Motor Oil (Synth)	1.3%	1.0%
	Screenwash	0.4%	0.4%
	Antifreeze	0.2%	1.5%
	Silicone Grease	0.3%	0.6%
	Petro Grease	1.8%	1.3%
	Battery Acid	3.0%	3.2%
	Petrol (Gasoline)	0.5%	0.6%
	Diesel	0.6%	0.5%



Tables of Final Results

PP Change in Dimensions and Weight - 168 hr Exposure (ASTM D453)

	Reagent	ZX % Change	XY % Change
Diameter	Dist Water	0.0%	0.0%
	Motor Oil (Synth)	0.0%	0.0%
	Screenwash	-0.6%	0.0%
	Antifreeze	-0.1%	-0.1%
	Silicone Grease	0.3%	0.4%
	Petro Grease	0.1%	0.1%
	Battery Acid	0.0%	-0.1%
	Petrol (Gasoline)	5.0%	4.4%
	Diesel	0.3%	0.3%
Thickness	Dist Water	0.6%	0.0%
	Motor Oil (Synth)	0.0%	-0.3%
	Screenwash	-0.1%	-0.3%
	Antifreeze	-0.1%	-0.3%
	Silicone Grease	1.3%	1.4%
	Petro Grease	0.4%	0.5%
	Battery Acid	-0.2%	-0.1%
	Petrol (Gasoline)	4.1%	5.5%
	Diesel	1.1%	0.2%
Weight	Dist Water	0.2%	0.1%
	Motor Oil (Synth)	1.1%	0.9%
	Screenwash	0.2%	0.2%
	Antifreeze	0.3%	0.1%
	Silicone Grease	2.3%	2.8%
	Petro Grease	2.6%	1.9%
	Battery Acid	0.5%	0.3%
	Petrol (Gasoline)	15%	15%
	Diesel	1.4%	1.3%
Weight (168hrs Dried)	Dist Water	0.0%	0.0%
	Motor Oil (Synth)	1.0%	0.9%
	Screenwash	0.0%	0.0%
	Antifreeze	0.6%	0.0%
	Silicone Grease	0.8%	1.0%
	Petro Grease	2.04%	1.6%
	Battery Acid	0.0%	0.0%
	Petrol (Gasoline)	3.7%	3.6%
	Diesel	0.7%	0.7%





PA11 Conclusions

Reagent	Weight & Dimension Stability	Mechanical Stability
Distilled Water	Excellent	Excellent
Synthetic Motor Oil	Excellent	Excellent
Screenwash	Excellent	Excellent
Antifreeze	Excellent	Excellent
Silicone Grease	Excellent	Excellent
Petroleum Grease	Excellent	Excellent
Battery Acid	Limited Chemical Resistance	Limited Chemical Resistance
Petrol (Gasoline)	Excellent	Excellent
Diesel	Excellent	Excellent

High Yield PA11 demonstrated excellent chemical resistance properties to seven of the nine reagents tested. The effects of distilled water, synthetic motor oil, screen wash, antifreeze coolant, silicone grease, petroleum grease, and diesel on the material were observed to be negligible. Battery acid caused mechanical strength reductions averaging -17% with a subsequent increase in elasticity due to softening of the material. Petrol immersion appears to also result in a plasticising effect.

While dimensional changes across all reagents were negligible, a notable gain in weight was observed in PA11 when immersed in battery acid. A permanent change in coloration from light gray to dark blue was also observed (Figure 7), the only test to undergo such a change.

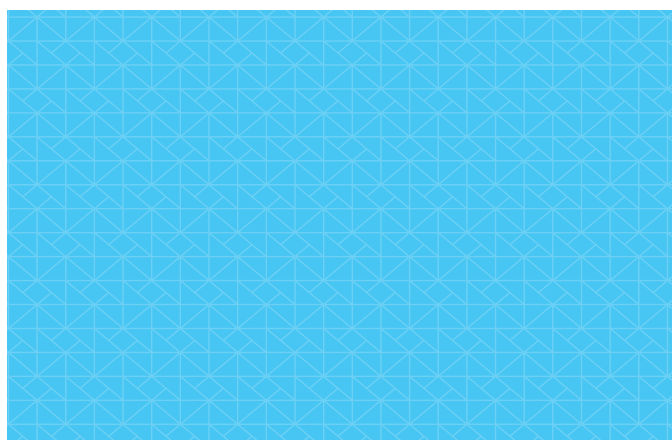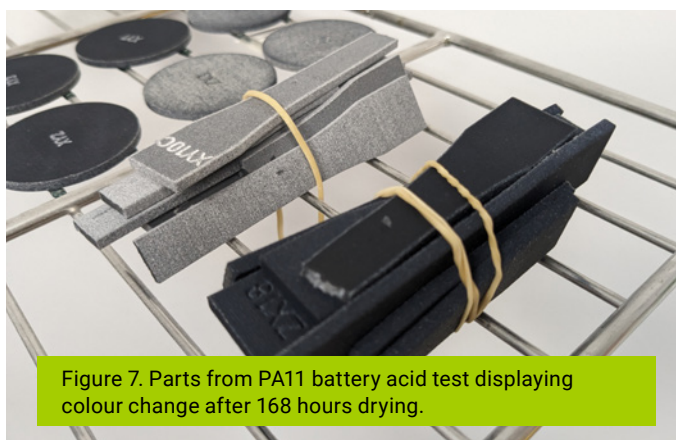



PA12 Conclusions

Reagent	Weight & Dimension Stability	Mechanical Stability
Distilled Water	Excellent	Excellent
Synthetic Motor Oil	Excellent	Excellent
Screenwash	Excellent	Excellent
Antifreeze	Excellent	Excellent
Silicone Grease	Excellent	Excellent
Petroleum Grease	Excellent	Excellent
Battery Acid	Good Chemical Resistance	Good Chemical Resistance
Petrol (Gasoline)	Excellent	Good Chemical Resistance
Diesel	Excellent	Excellent

SAF PA12 displayed excellent chemical resistance properties to seven of the nine reagents. The effects of distilled water, synthetic motor oil, screen wash, antifreeze coolant, silicone grease, petroleum grease, and diesel were observed to be insignificant.

PA12 only experienced a mild reduction in part strength alongside a slight decrease in elasticity when exposed to battery acid. Petrol immersion also displayed a similar mild reduction in mechanical properties.

All dimensional changes were negligible during this test. This material also displayed minimal increase in weight when exposed to battery acid, performing better than PA11 in this regard.



PP Conclusions

Reagent	Weight & Dimension Stability	Mechanical Stability
Distilled Water	Excellent	Excellent
Synthetic Motor Oil	Excellent	Excellent
Screenwash	Excellent	Excellent
Antifreeze	Excellent	Excellent
Silicone Grease	Good Chemical Resistance	Good Chemical Resistance
Petroleum Grease	Excellent	Excellent
Battery Acid	Excellent	Excellent
Petrol (Gasoline)	Limited Chemical Resistance	Limited Chemical Resistance
Diesel	Excellent	Excellent

SAF PP demonstrated excellent chemical resistance properties to seven of the nine reagents. The effects of distilled water, motor oil, screenwash, antifreeze, petroleum grease, battery acid, and diesel were observed to be negligible. As predicted, petrol significantly degraded the mechanical properties of this material. The results suggest a strong plasticising effect.

The material performed exceptionally exposed to battery acid (concentrated sulfuric), confirming it is currently the best suited SAF material for acidic applications.



stratasys

[stratasys.com](https://www.stratasys.com)
ISO 9001:2015
Certified

Stratasys Headquarters
7665 Commerce Way,
Eden Prairie, MN 55344
+1 800 801 6491 (US Toll Free)
+1 952 937-3000 (Intl)
+1 952 937-0070 (Fax)

1 Holtzman St., Science Park,
PO Box 2496
Rehovot 76124, Israel
+972 74 745 4000
+972 74 745 5000 (Fax)

WHITE PAPER
SAF

© 2024 Stratasys. All rights reserved. Stratasys, the Stratasys Signet logo, SAF, H350, GrabCAD and GrabCAD Print are registered trademarks of Stratasys Inc. All other trademarks are the property of their respective owners, and Stratasys assumes no responsibility with regard to the selection, performance, or use of these non-Stratasys products. Product specifications subject to change without notice.
WP_SAF_Chemical Resistance to Automotive Chemicals_A4_0624a